

腾龙芳烃（漳州）有限公司

Dragon Aromatics (Zhangzhou) Co.,Ltd. (DAC)


对二甲苯工程及整体公用配套工程

DAC PX Complex Project

加氢裂化装置

高压钢管采购规格书

Specification for high pressure service pipe

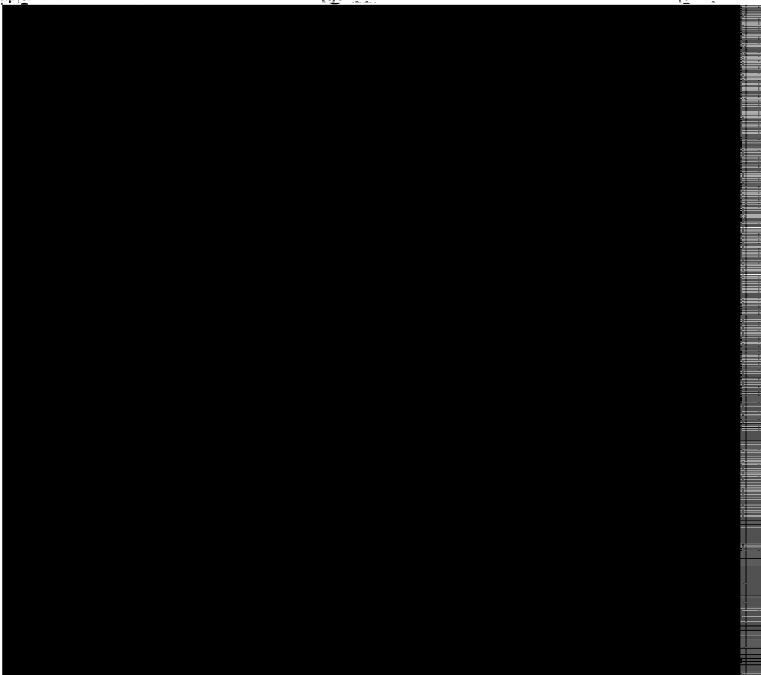

|           |            |                   |                   |                  |                   |     |                  |
|-----------|------------|-------------------|-------------------|------------------|-------------------|-----|------------------|
| C         |            |                   |                   |                  |                   |     |                  |
| B         |            |                   |                   |                  |                   |     |                  |
| A         | 2010.09    |                   | 王力军               | 王力军              | 王力军               | 王力军 |                  |
| 修改<br>REV | 日期<br>DATE | 说明<br>DESCRIPTION | 编制<br>PREPARED BY | 校核<br>CHECKED BY | 审核<br>APPROVED BY |     | 批准<br>ISSUED FOR |



SINOPEC ENGINEERING INCORPORATION

# 高压钢管采购规格书

编号(NO.)

修改(REV.): 0

PAGE 2 OF 13

## 目 录

|     |                                   |    |
|-----|-----------------------------------|----|
| 1   | 总则 GENERAL                        | 3  |
| 1.1 | 适用范围 SCOPE                        | 3  |
| 1.2 | 主要规范和标准（最新版本） STANDARDS AND CODES | 3  |
| 1.3 | 说明 EXPLAINING                     | 4  |
| 2   | 制造 MANUFACTURE                    | 4  |
| 3   | 热处理 HEAT TREATMENT                | 5  |
| 4   | 检查和试验 INSPECTION AND TESTING      | 6  |
| 5   | 标记和喷漆 MARKING AND PAINTING        | 9  |
| 6   | 包装和运输 PACKING AND SHIPPING        | 10 |

## 1 总则 GENERAL

### 1.1 适用范围 SCOPE

本规格书是关于高压钢管的最低要求, 除此以外还应满足相关标准的其他要求。

This specification is the basic technical requirement for steel pipes.

Manufacturer shall comply with relative standards except this

### 1.2 主要规范和标准 (最新版本) STANDARDS AND CODES

除非特别说明, 应使用下列标准的最新版本。

The latest edition of the following standards and codes shall be applied unless

otherwise noted.

ASTM A312 《无缝和焊接奥氏体不锈钢管 (P)》

Seamless and welded austenitic Stainless steel pipes

Seamless ferritic alloy steel pipe for high-temperature service

ASTM A106 《高温用无缝碳钢管 (P)》

Seamless carbon steel pipe for high-temperature service

Seamless and welded ferritic/austenitic stainless steel pipe

Nickel-Iron-Chromium-Molybdenum-Copper Alloy Seamless Pipe and Tube

ASTM A530 《专门用途碳钢和合金钢管通用要求》.

General requirements for specialized carbon and alloy-steel pipe

ASTM A370 《钢制品力学性能试验方法和定义标准》

Standard test methods and definitions for mechanical testing of steel

products

ANSI B31.3 《工艺管道》

Process piping

ANSI B36.10 《焊接和无缝锻钢钢管》

Welded and seamless wrought steel pipes

ANSI B36.19 《不锈钢管》

未经SEI书面许可, 不得以任何方式复制或用于与本项目无关的其它用途。

DO NOT REPRODUCE OR EMPLOY FOR OTHER PURPOSES OTHER THAN THIS PROJECT WITHOUT WRITTEN CONSENT FROM SEI.

Stainless steel pipe

MSS-SP-25 《阀门、管件、法兰和接头标准标记系统》标准标记系统

Standard Marking System for Valves, Fittings, Flanges and Unions

### 1.3 说明 EXPLAINING

本规格书以中文版为主，英文版仅供参考。

The Chinese version of specification has precedence to any English translation which  
is only for reference

## 2 制造 MANUFACTURE

2.1 冶炼过程由制造商完成。钢应采用电炉+AOD(氩氧炉精炼)或VOD(真空炉外精炼)。

Refining process shall be carried out by manufacturer. Steel shall be refined  
with electric furnace +AOD or VOD.

2.2 每炉都必须进行熔炼分析化学成分满足如下要求。

The heat analysis must be carried out for each furnace, chemical composition  
shall conform to the requirements of the following

| Material   | C          | S      | P       | N          | 其它成份 Other      |
|------------|------------|--------|---------|------------|-----------------|
|            |            |        |         |            | chemical        |
| 321, 316   | 0.04~0.08% | ≤0.02% | ≤0.03%  | N/A        | 其他成份满足相应        |
| 304L       | ≤0.03%     | ≤0.02% | ≤0.03%  | N/A        | ASTM 标准规定要求     |
| A106 Gr. B | ≤0.25%     | ≤0.02% | ≤0.03%  | N/A        | as per relevant |
| P11        | 0.05~0.15% | ≤0.02% | ≤0.012% | N/A        | ASTM standards  |
| P22        | 0.05~0.15% | ≤0.02% | ≤0.02%  | N/A        |                 |
| 2205       | ≤0.03%     | ≤0.02% | ≤0.02%  | 0.145~0.2% |                 |

2.3 所有钢管应为无缝钢管，并进行热加工。

Steel pipes shall be seamless and hot finished.

2.4 每根钢管长度最小为 6m，且供货长度应比料单中的实际长度至少长 1 米。

The length required for each pipe is 6 metres minimum, furthermore, the supplied  
length shall be 1 metre more than actual length in bill of material at least.

2.5 钢管表面的瑕点应通过修磨清除而不能用焊接修补。

The surface imperfection shall be removed with grinding and no any repair welding.

下表加工。

bevel ends of pipe shall be machined according to the following table.

| thickness                       | bevel ends           |
|---------------------------------|----------------------|
| $t \leq 22\text{mm}$            | ASME B16.25 Fig.2(A) |
| $22\text{mm} < t < 60\text{mm}$ | ASME B16.25 Fig.3(A) |

2.7 钢管以热处理状态供货。奥氏体不锈钢钢管要求用酸洗、钝化处理。

Steel pipes shall be delivered after the heat treatment. Pickling and passivation are required for Austenitic Stainless Steel.

2.8 壁厚偏差见附表: tolerance for wall thickness see table of material.

除特殊注明外, 如:  $0 \sim +25\%$ , 钢管的壁厚偏差应为  $-12.5\% \sim +12.5\%$ 。

Unless otherwise noted, for example:  $0 \sim +25\%$ , the wall thickness tolerance for all other pipe shall be  $-12.5\% \sim +12.5\%$ 。

2.9 321S.S 的钛含量应不少于 5 倍碳含量且不大于 0.7%。

The titanium content in 321S.S shall be not less than 5 times the carbon content and not more than 0.7%.

2.10 对2205双相不锈钢, 其点蚀当量PREN应不低于34 ( $\text{PREN} = \% \text{Cr} + 3.3\% \text{Mo} + 16\% \text{N}$ )。

For duplex stainless steel 2205, PREN should not less than 34 ( $\text{PREN} = \% \text{Cr} + 3.3\% \text{Mo} + 16\% \text{N}$ ) .

### 3 热处理 HEAT TREATMENT


3.1 碳钢要求正火处理, Cr-Mo 钢要求正火+回火或要求完全退火。

Normalizing heat treatment is required for carbon steel (A106B), Normalizing and tempering or full annealing are required for all Chrome-Molybdenum pipe.

3.2 321 不锈钢管加工完成后应进行固溶和稳定化热处理, 稳定化温度  $900^\circ\text{C} \pm 10^\circ\text{C}$ , 每 25mm 壁厚保温 2 小时 (4.7min/mm), 空冷。

未经SEI书面许可, 不得以任何方式复制或用于与本项目无关的其它用途。

DO NOT REPRODUCE OR EMPLOY FOR OTHER PURPOSES OTHER THAN THIS PROJECT WITHOUT WRITTEN CONSENT FROM SEI.

|                                                                                   |                  |                                                                                                      |
|-----------------------------------------------------------------------------------|------------------|------------------------------------------------------------------------------------------------------|
|  | <p>高压钢管采购规格书</p> | <p>编号(NO.) <span style="float:right">修改 (REV) : 0</span></p> <p>第 6 页 共 13 页</p> <p>PAGE 6 OF 13</p> |
|-----------------------------------------------------------------------------------|------------------|------------------------------------------------------------------------------------------------------|

Solution and stabilizing heat treatment are required after processing for 321.S.S. Stabilizing heat treatment shall be at a temperature 900±10℃, heat preservation time not less than 2 hours per 25mm wall thickness (4.7min/mm) and air cooling.

3.3 双相钢应按 ASTM A790 进行固溶处理。

Solution heat treatment is required for Duplex S.S. per ASTM A790.

3.4 凡热处理的部件应予以纪录并有热处理报告。

Heat treatment shall be recorded and its report is required.

#### 4 检查和试验 INSPECTION AND TESTING

4.1 根据 ASTM 标准，需对碳钢、合金钢和奥氏体不锈钢钢管进行成品分析。

4.2 每炉、每种钢管规格、每一热处理炉次的钢管需进行一次拉伸试验。

Tensile test shall be performed per each pipe size, heat of steel and heat treatment batch.

4.3 直径小于 2" 的钢管需进行弯曲试验，直径不小于 2" 的钢管需进行压扁试验。每炉、每种规格、每一热处理炉次的每种钢材必须从钢管两端取样。

Bending test is required for pipe smaller than NPS 2", and flattening test is required for pipes NPS 2" and larger. Specimen must be taken from both ends of pipe as per each material size, heat of steel and heat treatment batch.

4.4 根据 ASTM E381 规定，需对碳钢、合金钢和不锈钢钢管进行浸蚀试验。每种钢管分别按材料、规格、壁厚抽查 5%。

Carbon steel, Alloy steel and stainless steel pipe are required to be tested according to ASTM E381 etching. Etching tests shall show sound and reasonably uniform material free of injurious laminations, cracks, and similar

4.5 每批在两根管子上各取一个试样按 ASTM E45 进行非金属夹杂物检验：碳钢、合金钢钢管的

锈钢钢管非金属夹杂物  $A \leq 1.5$  级、 $B \leq 2.0$  级、 $C \leq 2.0$  级、 $D \leq 1.5$  级且  $A+B+C+D \leq 5$  级。

Nonmetallic inclusions shall be spot examined at two pipes for each batch per ASTM E45:

For carbon and alloy steel, nonmetallic inclusion A, B, C, D  $\leq$  level 2.5 respectively furthermore  $A+B+C+D \leq$  level 8.5; For stainless steel, nonmetallic inclusion A  $\leq$  level 1.0 B  $\leq$  level 2.0 C  $\leq$  level 2.0 D  $\leq$  level 1.5, furthermore  $A+B+C+D \leq$  level

b.

4.6 根据 ASTM A262 方法 E 及 ASTM A262 方法 G, 分别对经热处理炉冷的奥氏体不锈钢及双相不锈钢钢管在敏化状态下进行晶间腐蚀试验

For austenitic stainless steel and austenitic/ferritic stainless steel pipes, intergranular corrosion tests are required respectively according to

and testing is required on the sensitized condition.

4.7 对于不锈钢钢管, 按 ASTM E112 的方法测定平均晶粒度, 要求晶粒度为 5~7 级。

The grain size value for S.S. pipe as ASTM E112 shall be grade 5~7.

4.8 根据 ASTM E213 规定, 所有钢管需进行 100% 超声波检验, 槽断面形状见图 2 (B), 人工缺陷深度为壁厚的 5%, 但不能超过 1mm。

All pipe are required to be ultrasonic examined at the proportion of 100% according to ASTM E213, notch shape as Fig. 2(B), and notch depth shall be within 5% of wall thickness but not deeper than 1 mm.

钢管两端 100mm 长内外两侧, 对于不锈钢管进行 100% 液体渗透检验, 对于碳钢和合金钢管进行 100% 磁粉探伤

Inside and outside of nine ends for a length of 100mm, extension only, shall be tested by 100% PT for S.S. and by 100% MT for C.S. and A.S.

4.9 所有钢管都要进行水压试验, 对于奥氏体不锈钢管, 水中的氯离子不应超过 25ppm。

对于碳钢和合金钢管管, 水压试验引起的管道应力为一般屈服强度的 80%。对于奥氏体不锈钢管, 水压试验引起的管道应力为一般屈服强度的 70%。

Hydrostatic test is required for all pipes. For Austenitic Stainless, the chloride content in water shall be no more than 25 ppm. The stress of pipes caused by testing pressure shall be 80% of the normal yield strength for carbon steel and alloy steel, and 70% for Austenitic Stainless Steel.

4.10 材料测试证书(PMI)要求: 每炉或每一热处理炉批次的部件 5 件或少于 5 件全部测试; 6 件至 200 件按照 5%比例且不少于 5 件测试; 200 件以上按照 3%比例且不少于 10 件测试, 若代表性取样中的任一件不合格时, 应对该批次的全部组件进行检验。测试应作记录并立即标识“PMIV”。测试元素见下表。

| 材料             | 测试元素        | 材料           | 测试元素   |
|----------------|-------------|--------------|--------|
| 1 1/4Cr-1/2 Mo | Cr, Mo      | 2 1/4Cr-1 Mo | Cr, Mo |
| 304L           | C*, Cr, Ni, |              |        |
| 321            | Cr, Ni, Ti  |              |        |

\* 验证微量元素的适用方法: 特殊的实验室仪器, 适用的光学辐射分析仪, 可追溯的钢厂合格证结合使用地测量敏感度的化学分析。

The inspection sample shall be 100% for inspection lots of 5 pieces or less per heat of steel or heat treat batch. For inspection lots of 5 to 200 pieces, the inspection sample shall be 5% but not less than 5 pieces. For inspection lots greater than 200 pieces, the inspection sample shall be 3% but not less than 10 pieces. If any piece from a representative sample is found to be unacceptable, the remainder of that lot shall be examined 100%. PMI testing shall be recorded and marked “PMIV” immediately.

The alloy elements to be checked are as follow:

| Material       | Checked Alloy | Material     | Checked Alloy |
|----------------|---------------|--------------|---------------|
| 1 1/4Cr-1/2 Mo | Cr, Mo        | 2 1/4Cr-1 Mo | Cr, Mo        |
| 304L           | C*, Cr, Ni,   |              |               |
| 321            | Cr, Ni, Ti    |              |               |

\*

Suitable methods for identifying minor elements include: specialized laboratory instruments, chemical analysis using lower measurement sensitivity.

4.11 壁厚大于 25mm 的碳钢及合金钢管道, 每炉材料应进行一组 CVN 冲击试验, 三个试样在 0° 的平均冲击功不小于 18J, 其中最小值不小于 14J。



中国石化工程技术有限公司  
SINOPEC ENGINEERING INCORPORATION

## 高压钢管采购规格书

编号(NO.)

修改(REV.): 0

第 9 页 共 13 页

PAGE 9 OF 13

For carbon steel and Cr-Mo steel pipe, one set of CVN impact tests is required for each heat of material for wall thicknesses over 1.0" (25 mm). Impact energies at +32° F (0

C) must average greater than 15 ft-lb (18 joules) per set of 3 specimens, with a minimum value of 10 ft-lb (11 joules).

4.12 对 2205 双相不锈钢, 按照 ASTM E562 进行金相检测。铁素体含量应在 40~60%。

The content of ferrite of duplex 2205 steel as per ASTM E562 shall be 40~60%.

## 5 标记和喷漆 MARKING AND PAINTING

### 5.1 一般规定 GENERAL

5.1.1 所有钢管都应按相应的制造标准进行标记, MSS SP-25 应作为最低导则。

All pipe shall be marked in accordance with the standard to which they are manufactured, and MSS-SP-25 shall be used as the minimum requirement.

5.1.2 用于色标和标记的涂料不得含有任何有害金属或金属盐, 如锡、锌、铅、硫、铜或氯化物等在加热时可引起腐蚀的物质。且涂料应能抗盐水、热带环境或类似情况的腐蚀。

Paints or materials used for the color coding and stencil marking on components shall not contain a harmful metal, or metal salts, such as tin, zinc, lead, sulfur, copper or chlorides, which cause corrosive attack on heating and shall be resistant to salt water atmosphere, tropical or similar attack.

5.1.3 印记应使用低应力硬印模, 且印模应有至少 0.25mm 半径的圆头。

Marking by stamp shall be applied with low stress hard die stamping and a low stress stamp shall be round nosed with a radius of 0.25mm minimum.

5.1.4 标记必须清楚且不易毁坏。

Marking shall be clearly indicated and shall not be easily erased.

5.1.5 色标和标记绝不能用于下列部位:

Color coding and marking shall absolutely not be applied to the following locations:

|        |                      |
|--------|----------------------|
| 钢管的内表面 | Inside of pipe       |
| 螺纹     | Threads              |
| 焊缝和坡口  | Weld Seam and Bevels |

未经SEI书面许可, 不得以任何方式复制或用于与本项目无关的其它用途。

DO NOT REPRODUCE OR EMPLOY FOR OTHER PURPOSES OTHER THAN THIS PROJECT WITHOUT WRITTEN CONSENT FROM SEI.

密封面

Gasket Contact Surfaces

## 5.2 标记 MARKING

5.2.1 一般来说, 标记应包括下列各项, 且容易识别的符号。

Marking shall be carried out in general with regard to the following items using easily identifiable symbols.

公称直径

Nominal Size

壁厚 (Schedule Number) Wall Thickness (Schedule Number)

材料标准和级别 Material Specification and Grade

生产厂家名称 Manufacturer's Name or Trade Mark

装料号或炉号

Charge/Heat No.

通用性标记 Code as stated on Purchase Order

## 5.2.2 其它 OTHERS

a. 除本规范规定的以外, 其它标记应按相应的标准规范执行。

Identification marks other than those listed in this Specification shall be in accordance with the individual applicable specifications and standards.

b. 对难以标记的小尺寸物件, 应用不易脱落且注有识别物件的方法不标记。

Small bore items which would be difficult to mark shall have stainless steel labels

attached by stainless steel wire.

## 6 包装和运输 PACKING AND SHIPPING

6.1 钢管在检验和试验之后应放净水, 使其干燥。应提供足够的保护措施以防止运输中的机械损伤和海水大气腐蚀。

After inspection and test, pipe shall be completely free of water, dried and prepared for shipment. Adequate protection shall be provided against mechanical damage and atmospheric corrosion in transit.

6.2 钢管端部处应用坚实的木头、金属或塑料档板盖住或塞住, 以防损坏。

Pipe ends shall be covered or plugged with substantial wood, metal or plastic closures in order to avoid damage.

6.3 运输中钢管不能有任何损坏（包括碰伤、压扁、弯曲等）。

For all pipe, no damage can be made during shipments (No bending, colliding, pressing, etc).

6.4 包装由生产厂负责。

Packing shall be the responsibility of the manufacturer.

6.5 碳钢、合金钢和不锈钢管要分开装运，不得混装。

All stainless steel (S.S) pipes shall be kept away from carbon steel (C.S) and alloy steel (A.S) pipes, and packed respectively.

## 7 附表 1

### 料单中的缩写词

|            |                                     |           |
|------------|-------------------------------------|-----------|
| BC         | bolted cover                        | 螺栓连接的阀帽   |
| BLE        | bevel large end                     | 大端坡口      |
| BW         | butt welding                        | 对焊        |
| C. A.      | corrosion allowance                 | 腐蚀裕度      |
| CALC       | calculation                         | 计算(壁厚)    |
| COMM. CODE | commodity code                      | 编码        |
| CON        | concentric                          | 同心        |
| CS         | carbon steel                        | 碳钢        |
| DN         | nominal inside diameter             | 公称直径      |
| DSAW       | double submerged arc weld           | 双面埋弧焊     |
| ECC        | eccentric                           | 偏心        |
| EFW        | electric fusion welding             | 电熔焊       |
| FE         | female face                         | 凹面        |
| FLG        | flange                              | 法兰        |
| GRAF       | graphite                            | 石墨        |
| Gr         | grade                               | 等级        |
| HEX        | hexagonal                           | 六角        |
| IR         | inner ring                          | 内定位环      |
| LR         | long radius                         | 长半径       |
| ME         | male face                           | 凸面        |
| NPT        | national standard taper pipe thread | 60° 锥管内螺纹 |
| OCR        | octagonal ring gasket               | 八角环形垫片    |
| OD         | outside outer diameter              | 外径        |
| ID         |                                     | 控制内径      |
| OR         | outer ring                          | 外定位环      |

# 高压钢管采购规格书

编号(NO.)

修改(REV.): 0

第 13 页 共 13 页

PAGE 13 OF 13

|                |                                |           |
|----------------|--------------------------------|-----------|
| OR             | outer ring                     | 外定位环      |
| OS&Y           | outside screw and yoke         | 明杆支架型     |
| PBE            | plain both ends                | 两端平口      |
| PE             | plain end                      | 平口        |
| PPL            | Polyphenyl                     | 对位聚苯      |
| PSB            | pressure seal bonnet           | 压力密封阀盖    |
| PSE            | plain small end                | 小端平端      |
| R <sub>2</sub> | 55° taper pipe external thread | 55° 锥管外螺纹 |
| R <sub>1</sub> | 55° taper pipe internal thread | 55° 锥管内螺纹 |
| RF             | raised face                    | 突面        |
| RI             | ring joint face                | 环连接面      |
| TR             | threaded bonnet                | 螺纹连接的阀盖   |
| TBE            | threaded both ends             | 两端螺纹      |
| TFMP           | temperature                    | 温度        |
| TFWT           | tolerance for wall thickness   | 壁厚偏差      |
| THR            | thread                         | 螺纹        |
| TOE            | threaded one end               | 一端螺纹      |
| TRI-ECC        | TRI-eccentric                  | 三偏心       |
| SAW            | submerged arc weld             | 埋弧焊       |
| SMLS           | seamless                       | 无缝的       |
| SO             | slip-on                        | 平焊        |
| SR             | short radius                   | 短半径       |
| STL            | stellite                       | 司太立合金     |
| SS             | stainless steel                | 不锈钢       |
| SW             | socket welding                 | 承插焊       |
| WN             | welding neck                   | 对焊        |